


Corrosion of Steel in Concrete due to Carbonation

The high alkalinity of cement paste, approx. pH13, passivates the steel surface and protects it against oxidation (corrosion). The presence of chlorides, carbonation, acid attack or combination of all these, reduce pH of concrete and the reinforcing steel starts to corrode.

The Figure 1 shows the pH scale and divides it into three areas according to steel corrosion occurrence.


Figure 1. Corrosion of steel in concrete as a function of pH

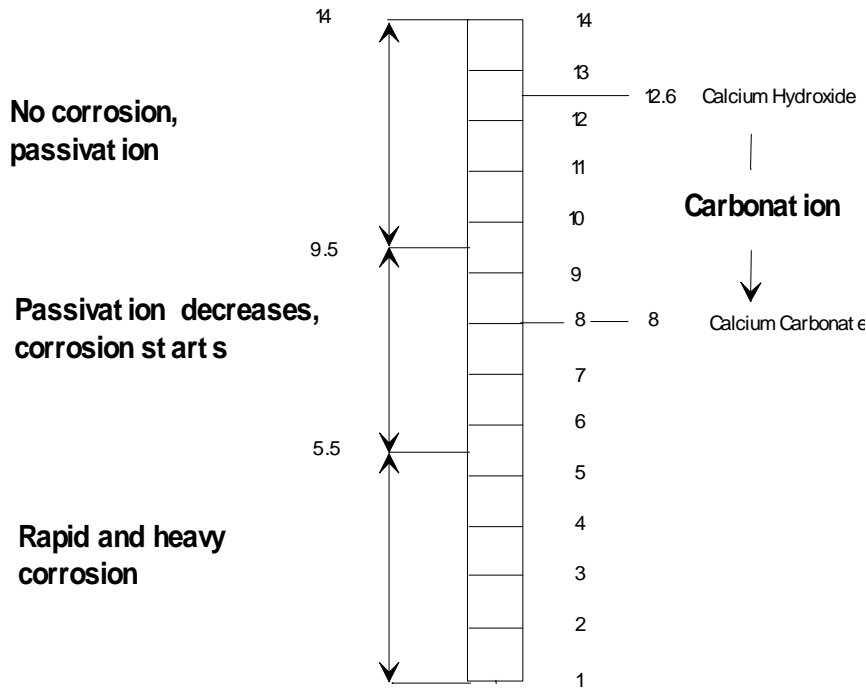

The high alkalinity of cement paste is primarily due to the high calcium hydroxide content (lime) the product of cement hydration as schematically shown in equation 1. Calcium silicate compounds (CS) contained in Portland cement, when mixed with water react and form hydrated calcium silicates (CSH) and Calcium Hydroxide (lime). Lime and other oxides of alkali earth elements, such Sodium (Na) and Potassium (K) create the highly alkaline environment of fresh or "young" concrete.



As concrete ages, lime reacts with the atmospheric carbon dioxide as shown in Equation 2.



This reaction "neutralizes" concrete and pH of concrete decreases. At pH level below 10 (approx. pH 9.5-9.6) the passivation protection of the steel surface due to the alkalinity of cement paste disappears and steel starts to corrode.

It has been shown (Ref.) that the depth of carbonation can be described by the following equation:

$$y := \sqrt{2 \cdot D \cdot \frac{C_1}{C_2} \cdot t} \quad \text{(eq.1),}$$

where

- y= depth of carbonation [mm]
- D= diffusion coefficient [mm²/a] (a=year)
- C₁= concentration of CO₂ in the air (approx. 0.6-0.8g/m³)
- C₂= amount of CO₂ to carbonate concrete (Approx. 10,000-50,000 g/m³)
- t = time [years]

The depth of carbonation as a function of time for different qualities of concrete is shown schematically in Fig. 2.

Figure 2. Depth of carbonation as a function of time for different qualities of concrete

Depth of Carbonation (mm)

Time (years)

If we assume that the carbon dioxide concentration for a given exposure area and the amount of carbon dioxide to react with lime in m³ of concrete are constants, then the equation 2 can be simplified an given as

$$y := \sqrt{C_c \cdot t} \quad \text{(eq. 2)}$$

where

- C_c = diffusion coefficient constant for a given concrete in a given environment.
- y= depth of carbonation [mm]
- t= time [years]

The equation 2 shows that the depth of carbonation is proportional to the root of carbonation time.

As an example we can look at the following case.

The depth of carbonation on a concrete structure was measured to be $y=6$ mm and the age of the structure is $t=10$ years. From this data we can determine the constant C_c .

$$C_c := \sqrt{2 \cdot D \cdot \frac{C_1}{C_2}}$$

$$C_c := \frac{y}{\sqrt{t}}$$

$$C_c = 3.162 \cdot a^{-\frac{1}{2}}$$

This means that this type of concrete will be carbonated to depth of 3.16 mm in one year. If the concrete cover for this type of concrete is 15 mm, then for the carbonation to reach this level it will take 22.5 years, as shown by equation 3.


$$t := \left(\frac{15}{C_c} \right)^2$$

$$t = 22.504 \cdot a$$

The advance of carbonation & the concrete reserve thickness for the same quality concrete is as shown below:

| Concrete Cover (y-mm) | 15 | 20 | 25 |
|---|-----------|-----------|-----------|
| Time for carbonation to reach steel (years) | 22.5 | 40 | 62.5 * a |
| Age of concrete (years) | 10 | 10 | 10 * a |
| Time of carbonation "reserve" (years) | 12.5 | 30 | 52.5 * a |

The thickness of concrete cover is very important - More concrete one has covering the steel, longer it will take before steel starts corroding.

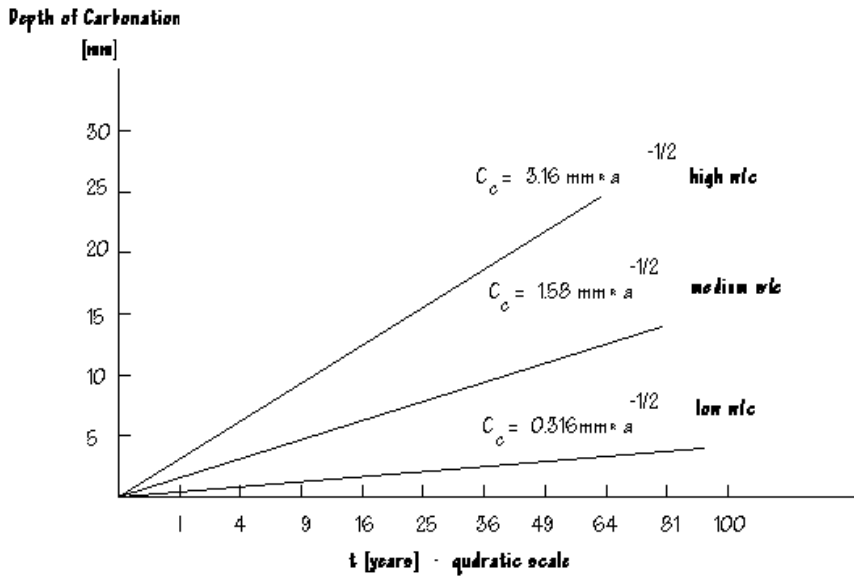

References on Carbonation of Concrete - Canada

1. Determine Potential of Carbonation of Concrete in Canada-State-of- the- Art, Literature Review, CMHC, 1987, John A. Bickley and Associates
2. Extent of Carbonation in Buildings in Toronto, CMHC, 1990, John A. Bickley and Associates
3. Anti-Carbonation Coatings for Use on Canadian Buildings, CMHC, 1992, Halsall and Associates
4. Concrete Carbonation in Canadian Buildings, CMHC, 1993, Halsall and Associates
5. Sorptivity Tests on Carbonated Concrete, CMHC, 1993, R.D. Hooton and Wayne Silberman

Key References on Carbonation of Concrete - Other

6. Carbonation Depths in Structural-Quality Concrete - an assessment of evidence from investigations of structures and from other sources, Currie R.J., Building Research Establishment Report, Building Research Station, Garston, Watford WD 2JR, Great Britain
7. A Review of Carbonation in Reinforced Concrete, Parrott L.J., Cement and Concrete Association, Wexham Springs, Slough SL3 5PL, Great Britain
8. Carbonization von beton, ihre Bedeutung und ihre Beeinflussung durch Beschichtungen (Carbonation of concrete, its significance and how it is affected by surface coatings), Engelfried, R., Defazet, 31, (1977), 9, 353-359
9. Die Carbonisation von Sichbeton und ihre Bekämpfung (Carbonation of concrete and how to combat it), Klopfer, H., Bautenschutz und Bausanierung, 3, (1987), 3, 86-97
10. Diffusionswiderstandszahlen für Kohlendioxid und Wasser und deren praktische Anwendung (Diffusion resistance factors for carbon dioxide and water and their practical significance), Engelfried, R., Farbe und Lack, 898 (1983), 7, 513-518
11. Stahlbeton-Schadensursachen, Schadensdiagnose Schutz und Instandsetzung (Reinforced concrete-Cause and diagnosis of deterioration, protection and repair), Weber, H., Wenderoth G., Expert verlag, 7032 Sindelfingen, 1986
12. Zur Frage der zulässigen Rissbreite und der erforderlichen Betondeckung im Stahlbetonbau unter besonderer Berücksichtigung der Karbonatisierung des Betons, Schiessl P., W.Ernst und Sohn, Berlin 1976, pp. 43-47.
13. Carbonization, Corrosion and Standardization, Parrott, L.J., Protection of Concrete, Proceedings of the International Conference held at the University of Dundee, Scotland, UK, September 1990, edited by Ravindra K. Dhir & Jeffrey W. Green, Chapman and Hall, 2-6 Boundary Road, London SE1 8HN

Gemite Group of Companies

E-mail: techinfo@gemite.com

Toll Free: 1-888-4-GEMITE (888-443-6483)

USA: 160-3840 E. Robinson Rd., Amherst NY 14228 Phone: 888-443-6483 Fax: 8884436329
CANADA: 1787 Drew Road, Mississauga ON L5S 1J5 Phone: 905-672-2020 Fax: 9056726780

Associated Companies Worldwide